



**BAKELITE**  
SYNTHETICS

## BreakThru™ TECHNOLOGY

# FOR PHENOLIC RESINS


Bakelite Synthetics phenolic products are used around the globe as a primary component of FRP composites, abrasives, filtration, honeycomb and in other industrial uses. Phenolic resins traditionally contain free formaldehyde levels ranging from 0.3% to greater than 1.5%. Reducing this residual formaldehyde is a frequent request to resin suppliers from manufacturers.

New proprietary BreakThru™ technology from Bakelite Synthetics addresses that desire. It has shown to lower formaldehyde in phenolic resins to below 1000ppm (or less than 0.1%) in laboratory analyses.

Extensive analyses of phenolic resins made with this proprietary technology comparing it to typical commercial resins, have shown the ability to significantly reduce free

formaldehyde as well as reduce free phenol while maintaining comparable cure profiles. In honeycomb applications, the new technology indicated performance improvements could also be possible. Water-based, the technology can also eliminate the use of solventborne resins in some applications.

## Traditional Free Formaldehyde Levels

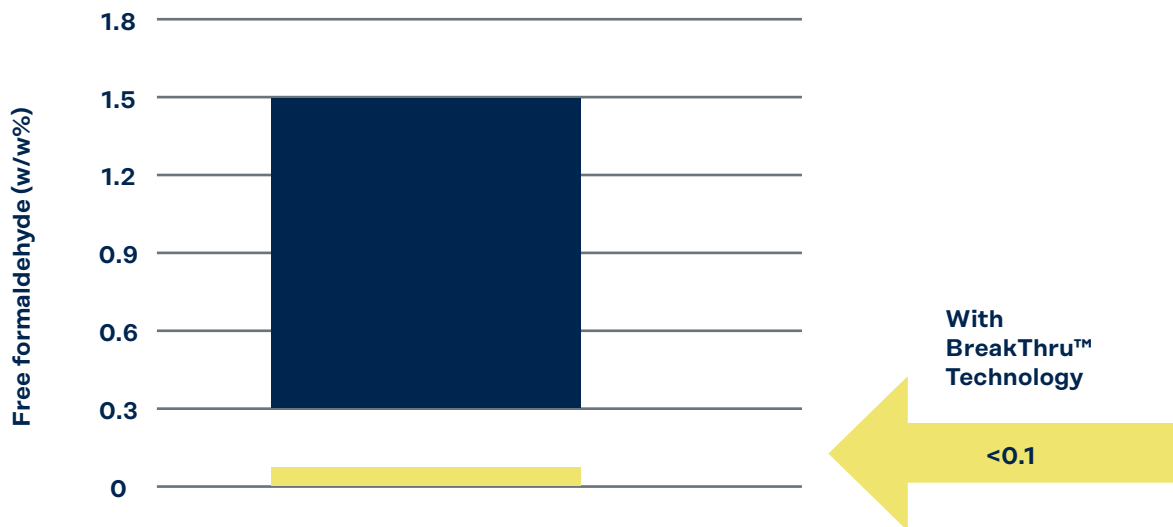

## Comparative Analyses Performed

The characterization of a typical commercial PF resin was compared to a phenolic resin with the new BreakThru™ technology utilizing:


**Thermal Analysis** - Differential Scanning Calorimetry and Dynamic Mechanical Analyzer to compare pre-cure, onset of cure, end of cure, cure

maximum temperatures, loss modulus maximum and tan delta maximum.


**Chromatography** - High-performance liquid chromatography and gas chromatography to compare free formaldehyde, free phenol and their molecular weights.

TYPICAL PROPERTIES	Commercial PF Resin (Control) (S1)	PF Resin with BreakThru™ Technology (S2)
Non-volatiles (w/w %)	75	75
Viscosity (cP)	2900	3520
pH	8.7	9.3
Free Formaldehyde (w/w%)	0.8	0.034
Free Phenol (w/w%)	5.6	4.6
Solvent	Water	Water


### Free Formaldehyde Content

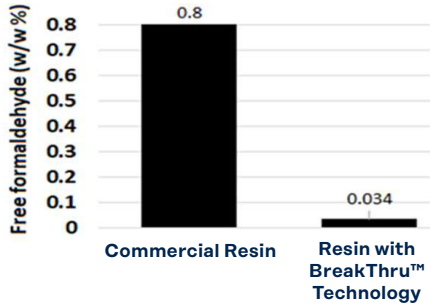


### Free Phenol Content

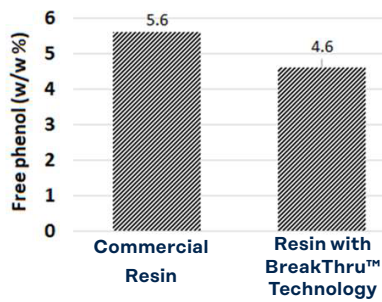


### Adjustable Molecular Weights

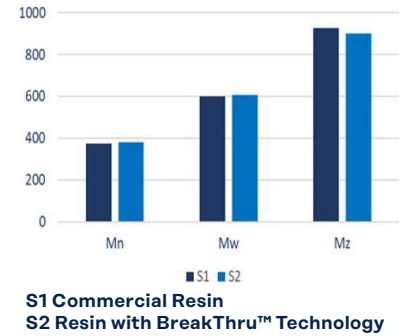

### Comparable Molecular Weight Distribution

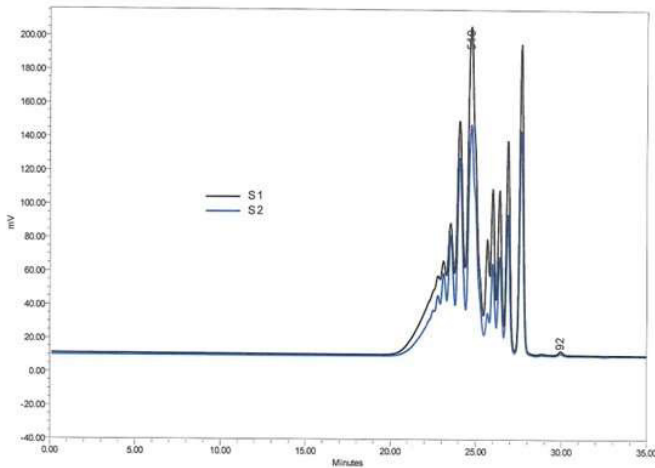

### Comparable Curing Heat Flow Performance

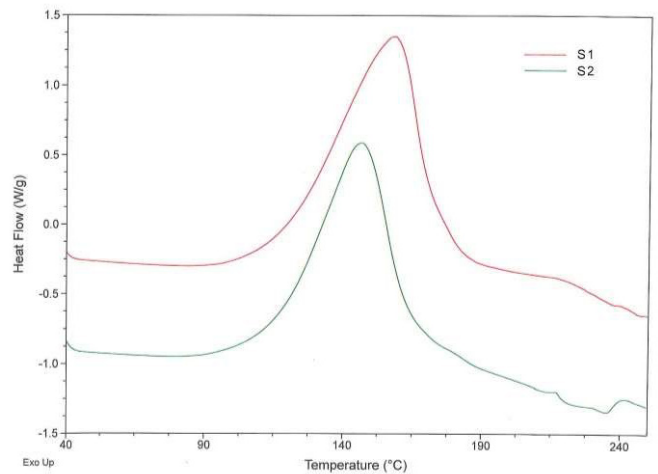

The curing profiles for the commercial resin and the BreakThru™ technology sample (S2) were comparable.


## HONEYCOMB ASSESSMENTS

A honeycomb assessment was performed between a waterborne resin with the BreakThru™ technology (S2) and a standard solventborne commercial phenolic resin (S3) used in honeycomb applications. The resin with BreakThru™ technology contained less free formaldehyde and less free phenol. Significantly, as a waterborne resin, using it as a replacement for solventborne resin carries additional advantages.

The compressive strength of the two resins were assessed. The testing showed the resin with BreakThru™ technology had improved compressive strength compared to that of the commercial resin, particularly at 40 % resin content. This study indicates

the new technology could provide improved performance.

### Compressive Strength

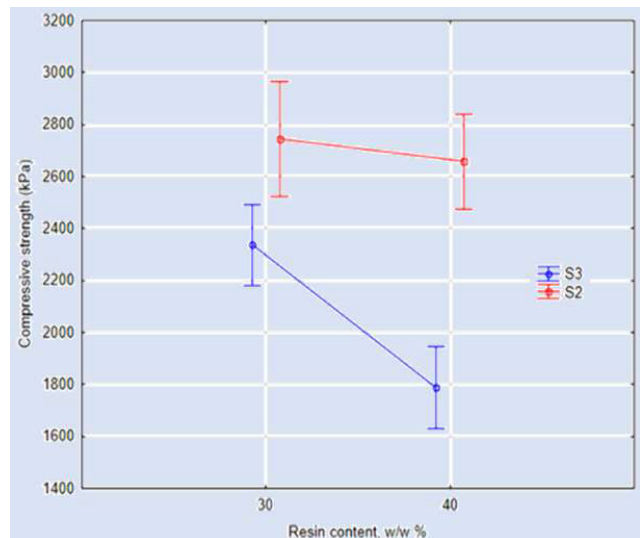



# Next Generation Synthetics

Infinite potential.  
Infinite curiosity.  
Infinite solutions.

Atlanta, GA  
Headquarters



Learn more about the vision, products  
and history of bakelite on our website

[bakelite.com](https://bakelite.com)

BAK-213 22/07

The information provided herein was believed by BAKELITE UK Holding Ltd. and its affiliated companies ("BAKELITE SYNTHETICS") to be accurate at the time of preparation or prepared from sources believed to be reliable, but it is the responsibility of the user to investigate and understand other pertinent sources of information, to comply with all laws and procedures applicable to the safe handling and use of the product and to determine the suitability of the product for its intended use. All products supplied by BAKELITE SYNTHETICS are subject to BAKELITE SYNTHETICS' terms and conditions of sale. BAKELITE SYNTHETICS MAKES NO WARRANTY, EXPRESS OR IMPLIED, CONCERNING THE PRODUCT OR THE MERCHANTABILITY OR FITNESS THEREOF FOR ANY PURPOSE OR CONCERNING THE ACCURACY OF ANY INFORMATION PROVIDED BY BAKELITE SYNTHETICS.

© 2022 BAKELITE. All rights reserved.  
® and ™ denote trademarks owned or licensed by BAKELITE SYNTHETICS.